

<https://doi.org/10.33472/AFJBS.6.6.2024.7328-7340>



African Journal of Biological Sciences

Journal homepage: <http://www.afjbs.com>



Research Paper

Open Access

## Microbially Induced Calcium Carbonate Precipitation (MICP) of Nature Expansive Soil to Evaluated Unconfined Compression Strength Parameter of Soil

Sitti Hijraini Nur<sup>1\*</sup>, Abd Rahman Djamaluddin<sup>2</sup>, Alif Candra Chlarah<sup>3</sup>

<sup>1\*,2</sup>Lecturer, Department of Civil Engineering, Hasanuddin University, Indonesia

<sup>3</sup>Undergraduate Student, Department of Civil Engineering, Hasanuddin University, Indonesia.

Corresponding Email: <sup>1\*</sup>[hijraininur@unhas.ac.id](mailto:hijraininur@unhas.ac.id)

### Article Info

Volume 6, Issue 6, July 2024

Received: 27 May 2024

Accepted: 25 June 2024

Published: 19 July 2024

*doi:* [10.33472/AFJBS.6.6.2024.7328-7340](https://doi.org/10.33472/AFJBS.6.6.2024.7328-7340)

### ABSTRACT:

Expansive soil is a type of soil that has a high potential for swelling and shrinkage. As a tropical country, Indonesia has two distinct seasons: the rainy and dry seasons. This condition affects expanded clay. During the dry season, the soil will shrink and crack due to reduced water, while in the rainy season, the soil will swell due to the increased water content in the soil. This study aims to determine the effect of Bio Grouting or MICP using *Bacillus subtilis* bacteria on changes in the mechanical properties of expansive soils. Expansive soil stabilization was carried out by adding bacterial solutions ranging from 3%, 4.5%, and 6%, where the bacterial cultures used were three days and six days of culture. Based on the study's results, it was found that the MICP method using the bacterium *Bacillus subtilis* could increase the value of unconfined compression strength. The optimum unconfined compression strength value was obtained in soil samples with the addition of 4.5% bacterial culture solution for six days with a curing period of 28 days of 16.46 kg/cm<sup>2</sup> or 51 times higher than the unconfined compression strength value of soil without stabilization.

© 2024 Sitti Hijraini Nur, This is an open access article under the CC BY license (<https://creativecommons.org/licenses/by/4.0/>), which permits unrestricted use, distribution, and reproduction in any medium, provided you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made

### 1. Background

In the general technical sense, the soil consists of aggregates (granules) of non-cemented (chemically bound) solid minerals and decomposed organic matter (including solid particles), which is defined as a material with liquids and gases that fills the space of solid particles.

Soil is an aggregate of mineral particles, air and water in a vacuum, they form a three-phase system [1,2].

Expansive soil is a type of soil that has a high potential for swelling and shrinkage. Expansive soil will experience expansion when there is an increase in water content [2,4,5], whereas when the water content decreases, there will be shrinkage [6].

Indonesia, as a tropical country, has two seasons, namely, the rainy season and the dry season. This condition will significantly affect expansive soil [7,8,9,10]. During the dry season, the soil will experience shrinkage and cracks due to reduced water, while during the rainy season, the soil will experience expansion due to increased water content in the soil [11,12,13,14,15,16].

Soil stabilization is a way to improve soil properties which is done by mixing other materials. Soil stabilization is an effort to improve the parameters of the soil shear strength so that the carrying capacity of the soil increases [17,18,19,20,21].

Jon A. Epps et al. (1971) explained that soil stabilization is an action to improve the engineering properties or characteristics of the soil (soil properties) [3].

Winterkorn (1975) states that Soil stabilization is a term for physical, chemical, or biological methods which can be used to improve specific properties of the soil to suit the proper engineering purposes [22,23,24].

Based on the addition of certain additives, soil stabilization processes are grouped into two, namely soil stabilization without additives (compaction) and soil stabilization with additives (cement, lime, bitumen, etc.) [25,26,27,28].

One of the environmentally friendly soil improvement methods is Bio Grouting. The influence of microorganisms on many minerals, such as carbonates, sulfates, phosphates, and silicates, has been proven. One of the standard processes in nature is Microbially Induced Calcium Carbonate (Calcite) Precipitation (MICP) [29,30]. MICP is a biologically driven calcium carbonate (calcite or  $\text{CaCO}_3$ ) deposition technology, which includes two biologically controlled and biologically induced  $\text{CaCO}_3$  deposition mechanisms [31,32,33]. In nature, biomineralization is a common phenomenon that occurs where mineral precipitation is formed by microbial activity. Among the various mechanisms involved in biomineral production, MICP has attracted the attention of engineers and microbiologists [34,35]. Microorganisms, which contain the enzyme urease, facilitate the precipitation of carbonates (by hydrolysis) [36,37,38]. One of the MICP systems is based on the urea hydrolysis process catalyzed by ureolytic bacteria, which can produce the enzyme urease [39,40]. The bacteria that can be used is *Bacillus subtilis* bacteria.

The use of *Bacillus subtilis* bacteria with a culture age of 6 days. The results showed that the California Bearing Ratio (CBR) and Unconfined Compressive Strength tests with the addition of 2%, 4%, and 6% bacteria showed that the compressive strength values tended to increase and decrease with the addition of 8% bacteria. The compressive strength curve also increased with the curing time of 3, 7, 14, and 28 days. This study's results indicate that using *Bacillus subtilis* as a stabilizing agent increases the carrying capacity of clay with high plasticity [41, 42].

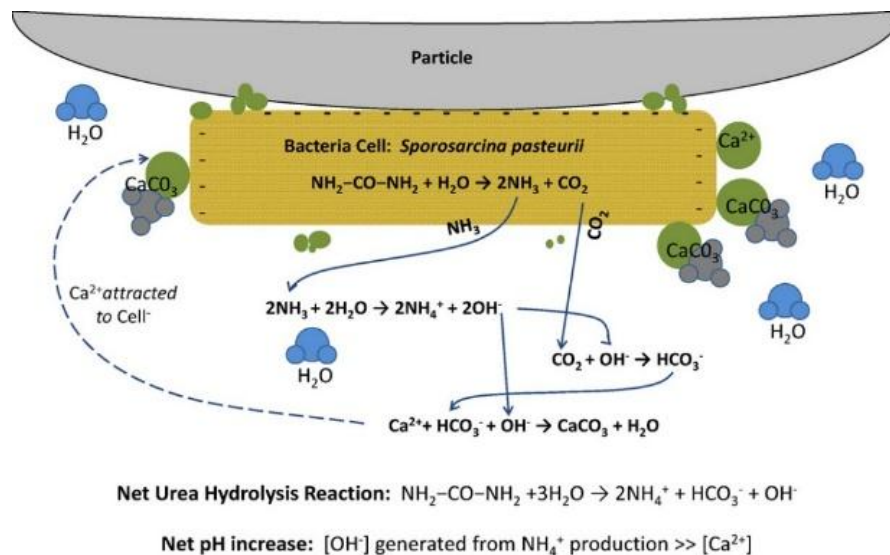


Figure 1. Biocementation Reaction Mechanism (Dejong et al., 2010).

Based on this, this research was conducted to explore the use of MICP as an environmentally friendly solution for research, especially in improving the mechanical properties of expansive soils.

## 2. Metodology

### a. Location and Time of Research

Location and Time of Research the soil used in the study was taken from Jalan Poros Bantimurung, Maros Regency, South Sulawesi Province.

At the Soil Mechanics Laboratory, Faculty of Engineering, Hasanuddin University, Gowa Regency, South Sulawesi, tests of the soil's mechanical and physical characteristics, the creation of the specimens, and the mechanical testing of the specimens were conducted. The intervals and durations established using the testing criteria are referred to as the research time.

### b. Expansive Soil Identification

There are several ways to identify expansive soil: direct and indirect. Direct identification is made using a free expansion test and an oedometer test. Indirect identification can be used using soil parameters such as Chen, Skempton, and Seed Method.

#### 2.2.1. Chen (1988)

Chen uses a single index, namely the Plasticity Index (PI) [12].

Table 1. Correlation of Plasticity Index Value with Level of Swelling Potential

Plasticity Index (PI) %	Swelling Potential
0 – 15	Rendah
10 – 35	Sedang
20 – 55	Tinggi
>55	Sangat tinggi

#### 2.2.1. Skempton (1953)

Identification of expansive clay is also often carried out by taking into account its activity value. Skempton (1953) defines activity as [13]:

$$Ac = \frac{PI}{C} \tag{1}$$

### 2.2.3. Seeds (1962)

This method uses a modified Skempton activity [14].

$$A_c = \frac{PI}{C - 10} \quad (2)$$

Seed et al. (1962) also proposed another empirical relationship between swelling potential and soil plasticity index.

$$S = 60K(PI)^{2.44} \quad (3)$$

### c. Method of Collecting Data

Data collection is carried out on the materials to be used for the manufacture of test objects. The first step is the selection of materials by taking into account their characteristics visually, then testing the characteristics of these materials to ensure their suitability with the required stabilizing agent.

The tests carried out in this study were to analyze the expansive soil behavior due to the bacterial stabilization process. The mechanical characteristics resulting from the Unconfined Compression Strength (UCS) were analyzed qualitatively to determine the function of the mixture composition and curing time. The mechanical test results are then used to determine the soil's effective expansive and bacterial composition.

Table 2. Physical and Mechanical Testing Standards

Test Type	ASTM
Specific Gravity	D854–14
Water Content	D2216–71
Atterberg Limits	D4318–05, D4943–08
Sieve Analysis and Hydrometer	D422–63
Compaction ( <i>Standard Proctor</i> )	D698–07
UCS ( <i>Unified Compression Strength</i> )	D2166–06

### d. Material

#### 2.4.1. Expansive Soil

The soil used in this study is expansive soil from Maros Regency, South Sulawesi Province.



Figure 2. Nature Expansive Soil

#### 2.4.2. *Bacillus Subtilis*

The bacterial culture process of *Bacillus subtilis* in this test was carried out on B4 medium with the formula Urea 20 gr; Nutrient Broth 3 gr; NaHCO<sub>3</sub> 2,12 gr; CaCl<sub>2</sub>.2H<sub>2</sub>O 4,14 gr; and NH<sub>4</sub>Cl 10 gr.

Then these ingredients are mixed into an Erlenmeyer flask with 1 liter of distilled water. *Bacillus subtilis* is cultivated with a culture age of 3 and 6 days, which will later be used as a stabilizing agent according to variations in the design of the test object.



Figure 3. *Bacillus subtilis*

#### 2.5. *Unconfined Compression Strenght*

Unconfined Compression Strength (UCS) is the axial pressure of the test object when it collapses or when the axial strain reaches 20%. An Unconfined Compression Strength test is one way to determine soil shear. The independent compressive strength test aims to determine the free compressive strength of a type of cohesive soil, both in its undisturbed, remolded, and compacted soil. UCS ( $q_u$ ) is the maximum axial stress value that a cylindrical specimen (soil sample) can be withstood before it collapses. UCS value is obtained from the reading of the proving ring dial with the maximum stress.

$$q_u = \frac{k \times R}{A} \quad (4)$$

This strength test measures how strong the soil is under the applied compressive strength until the soil is separated from its grains and also measures the strain of the soil due to the pressure.

### 3. Result and Discussion

#### a. *Characteristics of Physical and Mechanical Properties of Expansive Soil*

Testing the physical and mechanical characteristics of the soil was carried out to classify the type of soil used in the study. Based on the results and testing in the laboratory, the following data were obtained:

Table 3. Characteristics of Physical and Mechanical Properties of Soil

No.	Test Type	Unit	Test Result
<b>Physycal Properties</b>			
1.	Specific Gravity (Gs)	-	2,70
2.	Water Content ( $\omega$ )	(%)	72,00
3.	Atterberg Limits		
	Shrinkage Limit	(%)	13,88

	Plastic Limit	(%)	26,77
	Liquid Limit	(%)	82,75
	Plasticity Index	(%)	55,98
4.	<i>X-Ray Diffraction (XRD)</i>		
	Kaolinite	(%)	34,1
	Montmorillonite	(%)	1,7
5.	Sieve Analysis and Hydrometer Test		
	Gravel	(%)	0,40
	Sand	(%)	7,20
	Silt	(%)	22,40
	Clay	(%)	70,00
Classification			
USCS			CH
AASHTO			A-7-6
Mechanical Properties			
5.	Compaction (Kompasi)		
	Maximum Dry Density ( $\gamma_{dry\ max}$ )	gr/cm <sup>3</sup>	1,37
	Optimum Moisture Content ( $\omega_{opt}$ )	%	29,74
6.	UCS ( <i>Unconfined Compression Strength</i> )	kg/cm <sup>2</sup>	0,323
7.	Elastic Modulus	kg/cm <sup>2</sup>	8,730

Several methods are used to identify expansive soil indirectly.

### Chen

This method uses a single index, namely the Plasticity Index (PI). From the Atterberg boundary test, the plasticity index value is 55,98%. Based on Table 1, the soil has a high swelling potential because it has a plasticity index of >55%, so it can be said to be expansive soil.

### Skempton

Skempton identified expansive soils with activity values, namely the ratio between the plasticity index (PI) and the percentage of clay fraction (C). The activity value obtained was 0.8. Soil is included in the active category with moderate development potential, so it can be said to be expansive soil.

### Seed

Using equation (3) a potential swelling value of soil is 39,77%.

#### b. The Result of Unconfined Compression Strength test of Expansive Soil

##### Samples with Addition of Bacterial Culture 3 Days

##### a. Sample with 3% Bacterial Mix

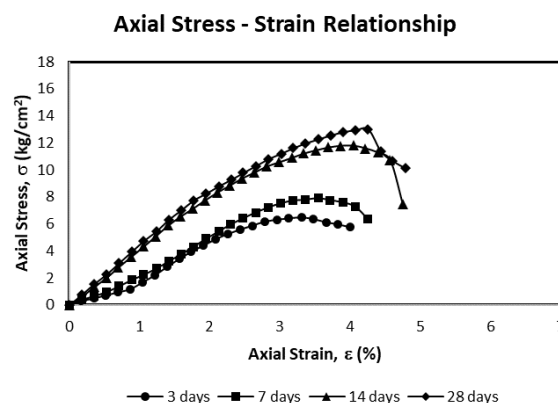


Figure 4. Graphics of Unconfined Compression Strength Test with the Addition of 3%

Bacterial Culture 3 Days

Based on variations in curing time for samples with the addition of 3% bacteria, there was an increase in UCS values during each curing period, namely 6.47 kg/cm<sup>2</sup> for 3 days curing, 7.90 kg/cm<sup>2</sup> for 7 days curing, 11.80 kg/cm<sup>2</sup> for 14 days curing, and 13.29 kg/cm<sup>2</sup> for 28 days curing.

b. Sample with 4,5% Bacterial Mix

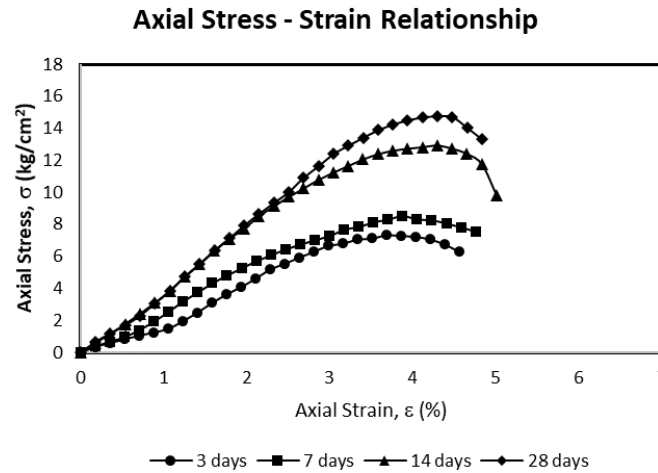


Figure 5. Graphics of Unconfined Compression Strength Test with the Addition of 4,5% Bacterial Culture 3 Days

Based on variations in curing time for samples with the addition of 4.5% bacteria, there was an increase in UCS values during each curing period, namely 7.34 kg/cm<sup>2</sup> for 3 days curing, 8.54 kg/cm<sup>2</sup> for 7 days curing, 12.94 kg/cm<sup>2</sup> for 14 days curing, and 14.78 kg/cm<sup>2</sup> for 28 days curing.

c. Sample with 6% Bacterial Mix

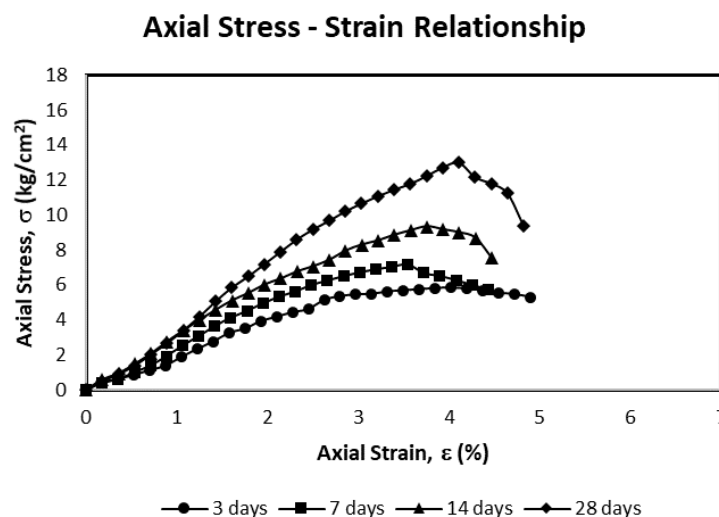


Figure 6. Graphics of Unconfined Compression Strength Test with the Addition of 6% Bacterial Culture 3 Days

Based on variations in curing time for samples with the addition of 6% bacteria, there was an increase in UCS values during each curing period, namely 5.83 kg/cm<sup>2</sup> for 3 days curing, 7.17 kg/cm<sup>2</sup> for 7 days curing, 9.34 kg/cm<sup>2</sup> for 14 days curing, and 13 kg/cm<sup>2</sup> for 28 days curing.

3.2.2. Samples with Addition of Bacterial Culture 6 Days

a. Sample with 3% Bacterial Mix

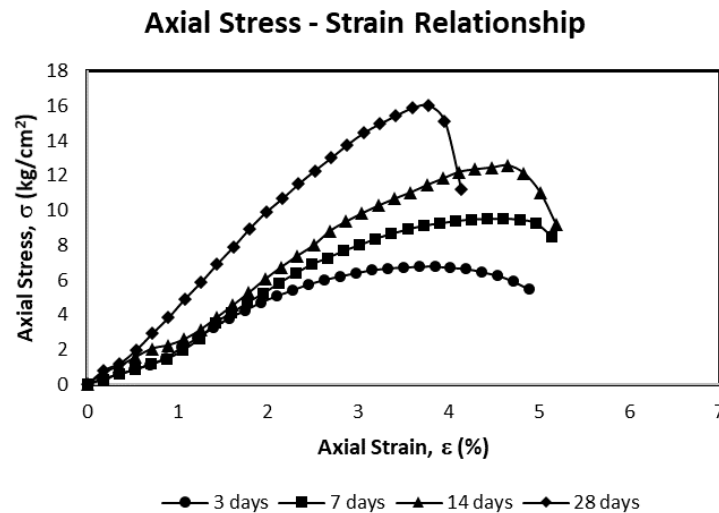


Figure 7. Graphics of Unconfined Compression Strength Test with the Addition of 3% Bacterial Culture 6 Days

Based on variations in curing time for samples with the addition of 3% bacteria, there was an increase in UCS values during each curing period, namely 6.79 kg/cm<sup>2</sup> for 3 days curing, 9.50 kg/cm<sup>2</sup> for 7 days curing, 12.58 kg/cm<sup>2</sup> for 14 days curing, and 16.02 kg/cm<sup>2</sup> for 28 days curing.

b. Sample with 4,5% Bacterial Mix


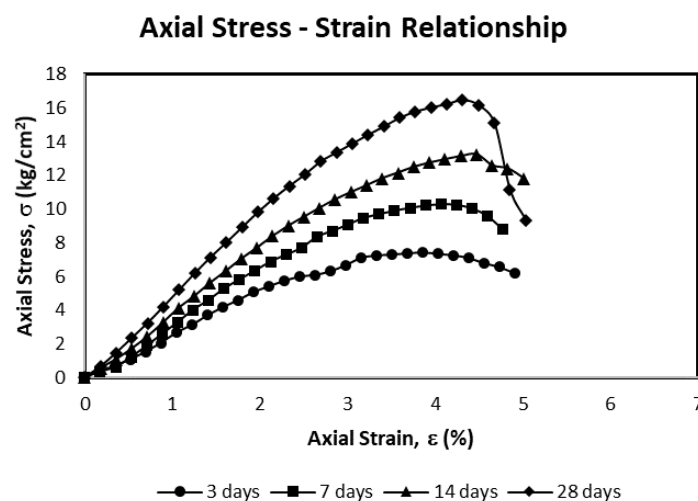


Figure 8. Graphics of Unconfined Compression Strength Test with the Addition of 4,5% Bacterial Culture 6 Days

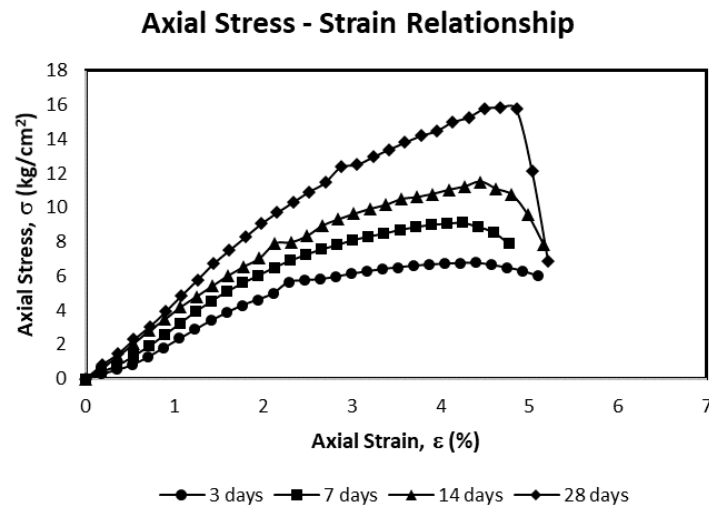

Based on variations in curing time for samples with the addition of 4.5% bacteria, there was an increase in UCS values during each curing period, namely 7.44 kg/cm<sup>2</sup> for 3 days curing, 10.27 kg/cm<sup>2</sup> for 7 days curing, 13.23 kg/cm<sup>2</sup> for 14 days curing, and 16.46 kg/cm<sup>2</sup> for 28 days curing.

c. Sample with 6% Bacterial Mix



**Figure 9.** Graphics of Unconfined Compression Strength Test with the Addition of 6% Bacterial Culture 6 Days

Based on variations in curing time for samples with the addition of 6% bacteria, there was an increase in UCS values during each curing period, namely 6.77 kg/cm<sup>2</sup> for 3 days curing, 9.12 kg/cm<sup>2</sup> for 7 days curing, 11.51 kg/cm<sup>2</sup> for 14 days curing, and 15.85 kg/cm<sup>2</sup> for 28 days curing.

3.2.3. Recapitulation of the Effect of Bacterial Mix on Unconfined Compression Strength of Expansive Soil

Table 4. Summary of Unconfined Compression Strength Test Results of Nature Expansive Soil Stabilized by Bacillus Subtilis

Sample	Culture	Bacterial Solution (%)	Unconfined Compression Strength, $q_u$ (kg/cm <sup>2</sup> )			
			3 Days	7 Days	14 Days	28 Days
Soil	3 Days	3	6.47	7.90	11.80	13.29
		4.5	7.34	8.54	12.94	14.78
		6	5.83	7.17	9.34	13.00
Soil	6 Days	3	6.79	9.50	12.58	16.02
		4.5	7.44	10.27	13.23	16.46
		6	6.77	9.12	11.51	15.85

Based on Table 4, it is found that the curing time affects the value of the UCS in the sample for each addition of the bacterial solution. Of the three variations of adding bacterial solution, namely 3%, 4.5%, and 6% with 3 and 6 days culture, it was found that the highest unconfined compression strength value was in the addition of 4.5% bacterial solution for 6 days culture.

#### 4. Conclusion

The addition of a stabilizing agent, namely a solution of *Bacillus subtilis* bacteria, can increase the unconfined compression strength of expansive soils. Of the three variations of the addition of bacterial solutions, namely 3%, 4.5%, and 6% with 3 and 6 days of culture, it was found that the highest UCS value was in the addition of 4.5% 6 days of bacterial culture solution. The effect of the curing period on stabilized samples of *Bacillus subtilis* is directly proportional, where the longer the curing time, the value of the UCS will also increase. From the results of the study, it was found that the optimum free compressive strength value was obtained during the 28 day curing period at 4.5% mixed bacterial culture 6 days of 16, 46 kg/cm<sup>2</sup> or 51 times higher than the soil without stabilization.

#### 5. References

1. Das, B. M., 2008. *Advanced Soil Mechanics*. London: Taylor & Francis.
2. Afrin, H., 2017. A Review on Different Types Soil Stabilization Techniques. *International Journal of Transportation Engineering and Technology*, 3(2), 19. <https://doi.org/10.11648/j.ijtet.20170302.12>
3. Jon A. Epps, Wayne A. Dunlap, Bob M. Galloway., 1971. *Basis for The Development of A Soil Stabilization Index System*. Reproduced by National Technical Information Science, Springfield, Vol. 2.
4. Winterkorn, H. F., 1957. *Granulometric and Volumetric Factors in Bituminous Soil Stabilization*. Proceedings, Highway Research Board, 1957.
5. Archibong, G. A., Sunday, E. U., Okeke, J. C., & Amadi, O. C., 2020. A review of the principles and methods of soil stabilization. *International Journal of Advanced Academic Research | Sciences*, 6(3), 89–115. <https://bit.ly/3mNUyRR>
6. Ghalandarzadeh, S., Montreal, P., Maghoul, P., Ghalandarzadeh, A., Courcelles, B., & Courcelles, B. B., 2022. Application of Nature-Based Nanotechnology for Enhancing Biocementation in Clay by Microbially Induced Calcium Carbonate Precipitation. <https://doi.org/10.21203/rs.3.rs-1509849/v1>
7. Mujah, D., Shahin, M. A., & Cheng, L., 2017. State-of-the-Art Review of Biocementation by Microbially Induced Calcite Precipitation (MICP) for Soil Stabilization. *Geomicrobiology Journal*, 34(6), 524–537. <https://doi.org/10.1080/01490451.2016.1225866>
8. Sugata, M., Widjajakusuma, J., Augestasia, A., Zacharia, A., & Tan, T. J., 2020. The use of eggshell powder as calcium source in stabilizing expansive soil using *Bacillus subtilis*. *Journal of Physics: Conference Series*, 1567(3). <https://doi.org/10.1088/1742-6596/1567/3/032058>
9. Ashraf, M. S., Azahar, S. B., & Yusof, N. Z., 2017. Soil Improvement Using MICP and Biopolymers: A Review. *IOP Conference Series: Materials Science and Engineering*, 226(1). <https://doi.org/10.1088/1757-899X/226/1/012058>
10. Yu, T., Souli, H., Péchaud, Y., & Fleureau, J. M., 2022. Optimizing protocols for microbial induced calcite precipitation (MICP) for soil improvement—a review. *European Journal of Environmental and Civil Engineering*, 26(6), 2218–2233. <https://doi.org/10.1080/19648189.2020.1755370>
11. Hasriana, Samang, L., Djide, M. N., & Harianto, T., 2018. A study on clay soil improvement with *Bacillus subtilis* bacteria as the road subbase layer. *International Journal of GEOMATE*, 15(52), 114–120. <https://doi.org/10.21660/2018.52.97143>
12. Chen, F.H. (1975;1988), *Foundation of Expansive Soils*, American Elsevier Science Publication, New York.

13. Skempton, A.W., 1953. The Colloidal Activity of Clays, Proc. 3rd Int.Conf. Soil Mech. Found. Eng. Switzerland, V.1, pp.57-61.
14. Seed, H.B., Woodward, R.J. & Lundgren, R., 1962. Prediction of Swelling Potential for Compacted Clay, Journal ASCE, Soil Mech. and Found. Div. Vol.88.
15. Achal, V., Mukherjee, A., Kumari, D., & Zhang, Q. (2015). Biomineralization for sustainable construction – A review of processes and applications. *Earth-Science Reviews*, 148, 1–17. <https://doi.org/10.1016/j.earscirev.2015.05.008>
16. Al-Thawadi, S., Cord-Ruwisch, R., & Info, A. (2012). Calcium Carbonate Crystals Formation by Ureolytic Bacteria Isolated from Australian Soil and Sludge. *Journal of Advanced Science and Engineering Research*, 2, 12–26. <https://www.researchgate.net/publication/230603445>
17. Anbu, P., Kang, C.-H., Shin, Y.-J., & So, J.-S. (2016). Formations of calcium carbonate minerals by bacteria and its multiple applications. *SpringerPlus*, 5(1), 250. <https://doi.org/10.1186/s40064-016-1869-2>
18. Barrima, A., Mashhour, I. M., & Amer, N. H. (2022). Effect of Bentonite Content on Hydraulic Conductivity of Sand-Bentonite Mixtures Used in Landfill Liners as an Alternative to Clay Liner in Egypt. *IOP Conference Series: Earth and Environmental Science*, 1056(1). <https://doi.org/10.1088/1755-1315/1056/1/012029>
19. Burbank, M., Weaver, T., Lewis, R., Williams, T., Williams, B., & Crawford, R. (2013). Geotechnical Tests of Sands Following Bioinduced Calcite Precipitation Catalyzed by Indigenous Bacteria. *Journal of Geotechnical and Geoenvironmental Engineering*, 139(6), 928–936. [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0000781](https://doi.org/10.1061/(ASCE)GT.1943-5606.0000781)
20. Cheng, L., & Cord-Ruwisch, R. (2014). Upscaling Effects of Soil Improvement by Microbially Induced Calcite Precipitation by Surface Percolation. *Geomicrobiology Journal*, 31(5), 396–406. <https://doi.org/10.1080/01490451.2013.836579>
21. Cheng, L., Cord-Ruwisch, R., & Shahin, M. A. (2013). Cementation of sand soil by microbially induced calcite precipitation at various degrees of saturation. *Canadian Geotechnical Journal*, 50(1), 81–90. <https://doi.org/10.1139/cgj-2012-0023>
22. Cheng, L., Shahin, M. A., & Cord-Ruwisch, R. (2017). Surface Percolation for Soil Improvement by Biocementation Utilizing In Situ Enriched Indigenous Aerobic and Anaerobic Ureolytic Soil Microorganisms. *Geomicrobiology Journal*, 34(6), 546–556. <https://doi.org/10.1080/01490451.2016.1232766>
23. Cheng, L., Shahin, M. A., & Mujah, D. (2017). Influence of Key Environmental Conditions on Microbially Induced Cementation for Soil Stabilization. *Journal of Geotechnical and Geoenvironmental Engineering*, 143(1). [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0001586](https://doi.org/10.1061/(ASCE)GT.1943-5606.0001586)
24. Chittoori, B. C. S., Burbank, M., & Islam, M. T. (2018). Evaluating the Effectiveness of Soil-Native Bacteria in Precipitating Calcite to Stabilize Expansive Soils. 59–68. <https://doi.org/10.1061/9780784481592.007>
25. Chittoori, B. C. S., Rahman, T., & Burbank, M. (2021). Microbial-Facilitated Calcium Carbonate Precipitation as a Shallow Stabilization Alternative for Expansive Soil Treatment. *Geotechnics*, 1(2), 558–572. <https://doi.org/10.3390/geotechnics1020025>
26. Chittoori, B. C. S., Rahman, T., Burbank, M., & Moghal, A. A. B. (2019). Evaluating Shallow Mixing Protocols as Application Methods for Microbial Induced Calcite Precipitation Targeting Expansive Soil Treatment. 250–259. <https://doi.org/10.1061/9780784482117.025>
27. Chu, J., Ivanov, V., Naeimi, M., Stabnikov, V., & Liu, H.-L. (2014). Optimization of calcium-based bioclogging and biocementation of sand. *Acta Geotechnica*, 9(2), 277–285. <https://doi.org/10.1007/s11440-013-0278-8>

28. Chu, J., Stabnikov, V., & Ivanov, V. (2012). Microbially Induced Calcium Carbonate Precipitation on Surface or in the Bulk of Soil. *Geomicrobiology Journal*, 29(6), 544–549. <https://doi.org/10.1080/01490451.2011.592929>
29. Feng, K., & Montoya, B. M. (2016). Influence of Confinement and Cementation Level on the Behavior of Microbial-Induced Calcite Precipitated Sands under Monotonic Drained Loading. *Journal of Geotechnical and Geoenvironmental Engineering*, 142(1). [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0001379](https://doi.org/10.1061/(ASCE)GT.1943-5606.0001379)
30. Fujita, Y., Taylor, J. L., Wendt, L. M., Reed, D. W., & Smith, R. W. (2010). Evaluating the Potential of Native Ureolytic Microbes To Remediate a 90 Sr Contaminated Environment. *Environmental Science & Technology*, 44(19), 7652–7658. <https://doi.org/10.1021/es101752p>
31. Hasriana, H. (2018). A STUDY ON CLAY SOIL IMPROVEMENT WITH BACILLUS SUBTILIS BACTERIA AS THE ROAD SUBBASE LAYER. *International Journal of GEOMATE*, 16(52). <https://doi.org/10.21660/2018.52.97143>
32. Indriani, A. M. (2021). BIOREMEDIATION OF COAL CONTAMINATED SOIL AS THE ROAD FOUNDATIONS LAYER. *International Journal of GEOMATE*, 21(84). <https://doi.org/10.21660/2021.84.j2124>
33. Li, M., Fang, C., Kawasaki, S., & Achal, V. (2018). Fly ash incorporated with biocement to improve strength of expansive soil. *Scientific Reports*, 8(1). <https://doi.org/10.1038/s41598-018-20921-0>
34. Li, X., Zhang, C., Xiao, H., Jiang, W., Qian, J., & Li, Z. (2021). Reducing Compressibility of the Expansive Soil by Microbiological-Induced Calcium Carbonate Precipitation. *Advances in Civil Engineering*, 2021. <https://doi.org/10.1155/2021/8818771>
35. Moraci, N., Busana, S., Cortellazzo, G., Favaretti, M., Mandaglio, M. C., & Schepis, M. (2018). Design and construction of a compacted clay liner in cover system of a municipal solid waste (MSW) landfill using nonstandard procedures. *Canadian Geotechnical Journal*, 55(8), 1182–1192. <https://doi.org/10.1139/cgj-2017-0371>
36. Mujah, D., Cheng, L., & Shahin, M. A. (2019). Microstructural and Geomechanical Study on Biocemented Sand for Optimization of MICP Process. *Journal of Materials in Civil Engineering*, 31(4). [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0002660](https://doi.org/10.1061/(ASCE)MT.1943-5533.0002660)
37. Mukherjee, S., Sahu, R. B., Mukherjee, J., & Sadhu, S. (2019). Application of Microbial-Induced Carbonate Precipitation for Soil Improvement via Ureolysis (hlm. 85–94). [https://doi.org/10.1007/978-981-13-0559-7\\_10](https://doi.org/10.1007/978-981-13-0559-7_10)
38. Mwandira, W., Nakashima, K., & Kawasaki, S. (2017). Bioremediation of lead-contaminated mine waste by *Pararhodobacter* sp. based on the microbially induced calcium carbonate precipitation technique and its effects on strength of coarse and fine grained sand. *Ecological Engineering*, 109, 57–64. <https://doi.org/10.1016/j.ecoleng.2017.09.011>
39. O’Leary, P. R., Canter, L., Robinson, W. D., Stone, R., Kahle, R., & Slutter, R. G. (1986). Land Disposal. Dalam the *Solid Waste Handbook* (hlm. 259–376). Wiley. <https://doi.org/10.1002/9780470172957.ch11>
40. Omar, R. C. (2018). STUDY OF BIO-GROUT TREATED SLOPE MODELS UNDER SIMULATED RAINFALL. *International Journal of GEOMATE*, 14(43). <https://doi.org/10.21660/2018.43.40742>
41. Sk, M. M., Ali, S. A., & Ahmad, A. (2020). Optimal Sanitary Landfill Site Selection for Solid Waste Disposal in Durgapur City Using Geographic Information System and Multi-criteria Evaluation Technique. *KN - Journal of Cartography and Geographic Information*, 70(4), 163–180. <https://doi.org/10.1007/s42489-020-00052-1>

42. Tobler, D. J., Maclachlan, E., & Phoenix, V. R. (2012). Microbially mediated plugging of porous media and the impact of differing injection strategies. *Ecological Engineering*, 42, 270–278. <https://doi.org/10.1016/j.ecoleng.2012.02.027>
43. Van Paassen, L. A., Ghose, R., van der Linden, T. J. M., van der Star, W. R. L., & van Loosdrecht, M. C. M. (2010). Quantifying Biomediated Ground Improvement by Ureolysis: Large-Scale Biogrout Experiment. *Journal of Geotechnical and Geoenvironmental Engineering*, 136(12), 1721–1728. [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0000382](https://doi.org/10.1061/(ASCE)GT.1943-5606.0000382)
44. Ye, S., Zeng, G., Wu, H., Zhang, C., Dai, J., Liang, J., Yu, J., Ren, X., Yi, H., Cheng, M., & Zhang, C. (2017). Biological technologies for the remediation of co-contaminated soil. *Critical Reviews in Biotechnology*, 37(8), 1062–1076. <https://doi.org/10.1080/07388551.2017.1304357>
45. Zhu, C., Vail, M., Tang, C. S., Anderson, L., Moroski, M., & Montalbo-Lomboy, M. T. (2019). Desiccation cracking behavior of MICP-treated bentonite. *Geosciences (Switzerland)*, 9(9). <https://doi.org/10.3390/geosciences9090385>